

doi: <https://doi.org/10.20546/ijcrar.2022.1006.002>

Synthesis of Silver, Copper and Zinc Nanoparticles from *Carica papaya* and *Annona muricata*, Seeds and Evaluation of their Antibacterial Activity

Prem Jose Vazhacharickal* and Jismon Thomas

Department of Biotechnology, Mar Augusthinose College, Ramapuram, Kerala-686576, India

*Corresponding author

Abstract

Nanotechnology is an emerging field of science. It has increased applications in diverse area for the development of new materials at nanoscale levels. Synthesis of nanoparticles using biological methods is referred as greener synthesis of nanoparticles. Seed extracts of papaya (*Carica papaya*) and Mullatha (*Annona muricata*) are used for the synthesis of silver, copper, and zinc nanoparticles. These plants have medicinal as well as antibacterial activity. Nanoparticles prepared from these seed extracts have antibacterial activity. Synthesized nanoparticles were characterized by UV-VIS Spectrophotometry. Silver nanoparticles shows maximum peak at 385 nm. Copper nanoparticles shows maximum peak at 680 nm. Zinc nanoparticles shows maximum peak at 350 nm. Synthesized silver, copper and zinc nanoparticles shows antibacterial activity against *Salmonella species*, *Pseudomonas species*, *Staphylococcus species*, *E. coli* and *Klebsiella species*. Antimicrobial assay was performed by agar well diffusion method using Muller Hinton agar media. when antibacterial activity of silver, copper and zinc nanoparticles from 3 different concentrations were observed, nanoparticles have 60 µl concentration shows maximum activity against these microbes. Silver nanoparticles shows greater antibacterial activity compared to silver nitrate and seed extract. Copper nanoparticles shows greater antibacterial activity compared to copper Sulphate and seed extract. Zinc nanoparticles shows greater antibacterial activity compared to zinc Sulphate and seed extract. Maximum zone of inhibition was at 60 µl for all the bacterial cultures. This green synthesis method is alternative to chemical method, since it is cheap, pollutant free and eco-friendly.

Article Info

Received: 02 May 2022

Accepted: 28 May 2022

Available Online: 20 June 2022

Keywords

Nanoparticles, *Carica papaya*, *Annona muricata*, Antimicrobial assay, Muller Hinton agar.

Introduction

Nanotechnology is an emerging field of science. It has increased applications in diverse area for the development of new materials at nanoscale levels (Paul *et al.*, 2015). Nano-technology mainly consists of the processing, separation, consolidation, and deformation of materials by one atom or one molecule (Prasad *et al.*, 2008). Nanoparticles has 1-100 nm in size and they possess novel physical and chemical properties

(Sajeshkumar *et al.*, 2015a; Sajeshkumar *et al.*, 2015b). Nanoparticles bear antibacterial properties (Hajipour *et al.*, 2012).

Green synthesis of nanoparticles

Synthesis of nanoparticles using biological methods is referred as greener synthesis of nanoparticles. Green synthesis provides advancement over chemical and physical method as it is cost effective, environment

friendly, and safe for human therapeutic use (Kumar *et al.*, 2009). Metals like silver, copper and zinc has inhibitory effect on microbes. Biological synthesis of metallic nanoparticles is inexpensive single step and eco-friendly methods.

The plants and seeds are used successfully in the synthesis of various greener nanoparticles such as copper, silver, and zinc oxide (Kuppusamy *et al.*, 2016; Mishra *et al.*, 2014).

Seed extracts of papaya (*Carica papaya*), Mullatha (*Annona muricata*), Passion fruit (*Passiflora edulis*), Eenth (*Cycas circinalis*), Egg fruit (*Pouteria campechiana*) are used for the synthesis of silver, copper, and zinc nanoparticles.

These plants have medicinal as well as antibacterial activity (Hernandez *et al.*, 2008; Prabu *et al.*, 2015; Vijaymeena *et al.*, 2013; Jageessar *et al.*, 2017; Peter *et al.*, 2014). Nanoparticles prepared from these seed extracts have antibacterial activity (Paul *et al.*, 2015; Showmya *et al.*, 2012).

Application of nanoparticles

Nanoparticles has various applications. Nanoparticles have been used for constructing electrochemical and biosensors (Luo *et al.*, 2006). Metal nanoparticles embedded paints have good antibacterial activity (Kumar *et al.*, 2008). Current research is going on regarding the use of magnetic nanoparticles in the detoxification of military personnel in case of biochemical warfare (Salata, 2005).

One of the major opportunities for nanoparticles in the area of computers and electronics is their use in a special polishing process, chemical-mechanical polishing or chemical mechanical planarization, which is critical to semiconductor chip fabrication (Elechiguerra *et al.*, 2005).

Magnetic nanoparticles are also used in targeted therapy where a cytotoxic drug is attached to a biocompatible nanoparticle for tumor cell treatment (Pankhurst *et al.*, 2003). Porous nanoparticles have been used in cancer therapy.

Bioremediation of radioactive wastes from nuclear power plants and nuclear weapon production such as uranium has been achieved using nanoparticles (Duran *et al.*, 2007).

Silver nanoparticles

Silver has long been recognized as having inhibitory effect on microbes present in medical and industrial process (Morones *et al.*, 2005; Lok *et al.*, 2007). The most important application of silver and silver nanoparticles is in medical industry such as topical ointments to prevent infection against burns and open wound.

Silver ions (Ag⁺) and its compounds are highly toxic to microorganisms exhibiting strong biocidal effects on many species of bacteria but have a low toxicity towards animal cells (Prema, 2011).

Objectives

Synthesis of silver, copper and zinc nanoparticles using seed extract of five different plants (papaya, Mullatha, canistel, Eenth, passion fruit) determine the antibacterial properties of these nanoparticles against *Escherichia coli* (*E. coli*), *Pseudomonas aeruginosa*, *Staphylococcus aureus*, *Salmonella typhi* and *Klebsiella pneumoniae*.

Scope of the study

The study would enlighten the medical and pharmaceutical applications various green synthesised nanoparticles applications against different microorganism which could be further explored.

Taxonomical classification (Mullatha)

Kingdom: Plantae-- planta, plantes, plants, vegetal

Subkingdom: Tracheobiota

Superdivision: Spermatophyta

Division: Magnoliophyta

Class: Magnoliopsida

Subclass: Magnoliidae

Order: Magnoliales

Family: Annonaceae

Genus: Annona L.

Species: *Annona muricata* L.

Taxonomical classification (Papaya)

Kingdom: Plantae-- planta, plantes, plants, vegetal

Subkingdom: Tracheobiota

Superdivision: Spermatophyta

Division: Magnoliophyta

Class: Magnoliopsida

Subclass: Dilleniidae

Order: Violales

Family: Caricaceae

Genus: *Carica* L.

Species: *Carica papaya* L.

Seed extracts of papaya (*Carica papaya*) and Mullatha (*Annona muricata*) are used for the synthesis of silver, copper, and zinc nanoparticles. These plants have medicinal as well as antibacterial activity (Hernandez *et al.*, 2008; Prabu *et al.*, 2015; Vijaymeena *et al.*, 2013; Jageessar *et al.*, 2017; Peter *et al.*, 2014). Nanoparticles prepared from these seed extracts have antibacterial activity (Paul *et al.*, 2015; Showmya *et al.*, 2012). A nanoparticle has lot of scope for health care products such as burn dressings, antimicrobial applications, medical devices and scaffolds (Mishra *et al.*, 2014).

Seeds of papaya (*Carica papaya*) contains many phytochemical compounds like flavonoids and phenolics, these compounds are responsible for their antimicrobial property (Muhamad *et al.*, 2016).

The papaya (*Carica papaya*) tree belongs to a small family caricaceae, having four genera in the world. Papaya contains broad spectrum of phytochemicals including, polysaccharides, minerals, enzymes, proteins, alkaloids, glycosides, fat and oils, lectins saponins, flavonoids and steroids (Krishna *et al.*, 2008; Ayoola *et al.*, 2010).

Papaya seed is used for different nanoparticle synthesis. Silver nanoparticles are synthesized by using papaya seed as a reducing agent (Kale *et al.*, 2018). Papaya seed is also used for the synthesis of copper and zinc nanoparticles. During copper nanoparticle synthesis,

copper salts were used as basic precursors and seed extract act as a stabilizer (Singh, 2017).

Mullatha (*Annona muricata*) belongs to the family of annonaceae has a widespread pantropical distribution and has been proudly known as corossol. Leaves and seeds of this species containing a great number of acetogenins. Such isolated compounds have some antitumoral, cytotoxicity and pesticidal properties. It contains esters, terpenes, alcohol, aldehydes, ketones, aromatic compounds, hydrocarbons and lactones (Rajeswari *et al.*, 2012).

Seed extracts of papaya (*Carica papaya*) and Mullatha (*Annona muricata*) are used for the synthesis of silver, copper, and zinc nanoparticles. Copper nanoparticles widely used due to their superior, optical, electrical, antifungal/antibacterial and biomedical applications. Copper nanoparticles have superior antibacterial activity as compared to silver nanoparticles. Because copper is highly toxic to microorganisms (Singh, 2017).

The antimicrobial activity mainly tested for drug discovery and prediction of therapeutic outcome. Agar disc diffusion and agar well diffusion are two methods used to evaluate antimicrobial activity (Balouiri *et al.*, 2016).

Feng *et al.*, (2000) conducted a study to observe the effects of silver ions on gram-positive (*Staphylococcus aureus*) and gram-negative bacteria (*Escherichia coli*). Under TEM they observed that cells exposed to the Ag⁺ ions seemed to have activated a stress response that led to the condensation of DNA in the center of the cell. They also observed cell membrane detachment from the cell wall, cell wall damage, and electron dense granules outside and, in some instances, inside the cell. It was proposed that condensation of DNA occurred as a protective measure in order to protect the genetic information of the cell (Feng *et al.*, 2000), however condensation of DNA could also prevent cell replication by preventing the DNA from being accessed by transcriptional enzymes such as DNA polymerase. The electron dense granules that formed inside and outside the cell were extracted and subjected to X-ray microanalysis to determine their composition. It was found that the granules were in part composed of silver and sulfur. This finding supports the idea that silver inactivates proteins by binding to sulfur-containing compounds (Klueh *et al.*, 2000). It was also observed that when treated with Ag⁺, *E. coli*, a gram-negative bacterium, sustained more structural damages than the

gram-positive *Staphylococcus aureus* (Feng *et al.*, 2000). It was also reported that treating cells with silver leads to cell shrinkage and dehydration (Guggenbichler *et al.*, 1999).

Studies shows that silver nanoparticles anchor to and penetrate the cell wall of Gram-negative bacteria (Morones *et al.*, 2005), it is reasonable to suggest that the resultant structural change in the cell membrane could cause an increase in cell permeability, leading to an uncontrolled transport through the cytoplasmic membrane, and ultimately cell death. It has also been proposed that the antibacterial mechanism of silver nanoparticles is related to the formation of free radicals and subsequent free radical-induced membrane damage (Danilczuk *et al.*, 2006; Kim *et al.*, 2007).

Novel wound dressings have been developed that use silver to help prevent wound infections (Joshua *et al.*, 2008). Silver nanoparticles are incorporated into the wound dressing, and the silver-enhanced wound dressings were found in vitro to consistently kill *Pseudomonas aeruginosa* cultures entirely and kill *Staphylococcus aureus* cultures with >99.99% efficiency (Ong *et al.*, 2008). In mice, the silver-enhanced wound dressings were also found to reduce mortality from *Pseudomonas aeruginosa* wound infections from 90% to 14.3% (Ong *et al.*, 2008).

Studies revealed the antibacterial properties of surgical masks coated with silver nanoparticles (Li *et al.*, 2006). Nanoparticle coated masks were capable of a 100% reduction in viable *Escherichia coli* and *Staphylococcus aureus* cells after incubation. Additionally, the study reported no signs of skin irritation in any of the persons wearing the masks (Li *et al.*, 2006).

Silver nanoparticles have been used to impart antimicrobial activity to cotton fibres. Cotton samples were immersed in silver nanoparticle solutions and then subjected to a curing process to allow the nanoparticles to adhere to the cotton (El-Rafie *et al.*, 2010). A chemical binder was then applied to the fabric to help maintain nanoparticle-cotton binding. Cotton samples prepared in this manner were able to reduce *Staphylococcus aureus* and *Escherichia coli* cell counts by 97% and 91% respectively. Even after subjecting the fabric to 20 laundry cycles, the cotton samples were still able to reduce *Staphylococcus aureus* and *Escherichia coli* cell counts by 94% and 85% respectively. Cotton prepared in this manner could be used by individuals working in the medical field or those who often work

with microbes to prevent the spread of infectious bacteria (El-Rafie *et al.*, 2010).

In the past few decades, researchers are taking interest in the development of textile fabrics containing antibacterial agents. As, silver is non-toxic and possesses antimicrobial properties it has encouraged workers to use silver nanoparticles in different textile fabrics. In this direction, silver nanocomposite fibres were prepared containing silver nanoparticles incorporated inside the fabric but from the scanning electron microscopic study it was concluded that the silver nanoparticles incorporated in the sheath part of fabrics possessed significant antibacterial property compared to the fabrics incorporated with silver nanoparticles in the core part (Yeo and Jeong, 2003).

Toxicity from silver is observed in the form of argyria, only when there is a large open wound and large amount of silver ions are used for dressing. There are no regular reports of silver allergy (Leaper, 2006). Silver nanoparticles in most studies are suggested to be non-toxic. But due to their small size and variable properties they are suggested to be hazardous to the environment (Braydich-Stolle *et al.*, 2005). Hussain *et al.*, (2005) studied the toxicity of different sizes of silver nanoparticles on rat liver cell line (BRL 3A) (ATCC, CRL-1442 immortalized rat liver cells). The authors found that after an exposure of 24 hour the mitochondrial cells displayed abnormal size, cellular shrinkage and irregular shape. Cytotoxicity study of silver nanoparticle impregnated five commercially available dressings was undertaken by Burd *et al.*, (2007). In the study, it was found that three of the silver dressings depicted cytotoxicity effects in keratinocytes and fibroblast cultures. Braydich-Stolle *et al.*, (2005) reported the toxicity of silver nanoparticles on C18-4 cell, a cell line with spermatogonial stem cell characteristics. From the study, it was concluded that the cytotoxicity of silver nanoparticles to the mitochondrial activity increased with the increase in the concentration of silver nanoparticles.

Silver has been known to possess strong antimicrobial properties both in its metallic and nanoparticle forms hence; it has found variety of application in different fields. The Fe₃O₄ attached Ag nanoparticles can be used for the treatment of water and easily removed using magnetic field to avoid contamination of the environment (Gong *et al.*, 2007). Silver sulfadiazine depicts better healing of burn wounds due to its slow and steady reaction with serum and other body fluids (Fox and Modak, 1974). The nanocrystalline silver dressings,

creams and gels effectively reduce bacterial infections in chronic wounds (Richard *et al.*, 2002; Leaper, 2006; Ip *et al.*, 2006).

The silver nanoparticle containing poly vinyl nano-fibers also show efficient antibacterial property as wound dressing (Jun *et al.*, 2007). The silver nanoparticles are reported to show better wound healing capacity, better cosmetic appearance and scarless healing when tested using an animal model (Tian *et al.*, 2006). Silver impregnated medical devices like surgical masks and implantable devices show significant antimicrobial efficacy (Furno *et al.*, 2004).

Environmental-friendly antimicrobial nanopaint can be developed (Kumar *et al.*, 2008). Inorganic composites are used as preservatives in various products (Gupta and Silver, 1998). Silica gel micro-spheres mixed with silica thio-sulfate are used for long lasting antibacterial activity (Gupta and Silver, 1998). Treatment of burns and various infections (Feng *et al.*, 2000). Silver zeolite is used in food preservation, disinfection and decontamination of products (Matsuura *et al.*, 1997; Nikawa *et al.*, 1997). Silver nanoparticles can be used for water filtration (Jain and Pradeep, 2005).

Hypothesis

The current research work is based on the following hypothesis

Seeds of papaya (*Carica papaya*) and Mullatha (*Annona muricata*) could be used as antibacterial agents.

These seed extracts could be used in formulating nanoparticles (silver, copper and zinc) and their antibacterial activity vary widely.

Materials and Methods

Study area

Kerala state covers an area of 38,863 km² with a population density of 859 per km² and spread across 14 districts. The climate is characterized by tropical wet and dry with average annual rainfall amounts to 2,817 ± 406 mm and mean annual temperature is 26.8°C (averages from 1871-2005; Krishnakumar *et al.*, 2009). Maximum rainfall occurs from June to September mainly due to South West Monsoon and temperatures are highest in May and November.

Sample collection

Seeds of Mullatha and papaya were collected from Thankamany, Idukki district of Kerala state, India. The seeds were thoroughly cleaned using double distilled water. The samples were collected in poly ethylene zipper bags, later washed two times with distilled water and stored in polyethylene zipper bags and processed in the laboratory.

The samples were dried in hot air oven at 60°C for 48hrs. The samples were finely powdered using a kitchen blender (Prestige Nakshatra plus, Prestige industries Mumbai) and later stored in air tight polyethylene zipper bag for analysis.

Extraction method

The seeds of papaya and Mullatha are powdered. Then 10g of each powdered seed sample is dissolved in 50 ml distilled water, the contents are mixed thoroughly using a mortar and pestle and filtered using a filter paper, thus filtered solution is taken as the extract. The extract was then stored at 4°C after covering the beaker with aluminum foil for further use. The obtained seed extract which appeared light yellowish in color was stored 4°C for further use.

Synthesis of nanoparticles

Silver nanoparticles

Stock solution was prepared by dissolving 1mM silver nitrate (AgNO₃; Merck, Mumbai, India) and volume made up to 250 ml with distilled water. 10 ml of seed extract of different plants (papaya, Mullatha, Eenth, canistel and passion fruit separately) was added to 90 ml of 1mM AgNO₃ solution and allowed to react at room temperature.

Copper nanoparticles

Stock solution was prepared by dissolving 2.49 g Copper sulphate (CuSO₄) and volume made up to 100 ml with distilled water. 10 ml of seed extract of different plants (papaya, Mullatha, Eenth, canistel and passion fruit separately) was added to 90 ml of 100 mM CuSO₄ and allowed to react at room temperature.

Zinc nanoparticles

Stock solution was prepared by dissolving 2.87 g Zinc sulphate ($ZnSO_4$) and volume made up to 100 ml with distilled water. 10 ml of seed extract of different plants (papaya, Mullatha, Eenth, canistel and passion fruit separately) was added to 90 ml of 100 mM $ZnSO_4$ solution and allowed to react at room temperature.

Test microorganisms

The organism used comprise of 4 gram-negative organisms (*E. coli*, *Klebsiella*, *Salmonella* and *Pseudomonas*) and one gram-positive organism (*Staphylococcus*). The test organisms were obtained from the department of Biotechnology, Mar Augusthinose College, Ramapuram.

Escherichia coli

These are gram negative, facultative or anaerobic rods (commonly abbreviated *E.coli*) commonly found in the lower intestine of warm blooded organisms. The organisms are relatively heat sensitive and are readily destroyed at high temperature. The optimal temperature for growth is 37°C. *E. coli* is responsible for intestinal tract infection and diarrhoea.

Staphylococcus species

These are spherical in shape, non-motile, gram positive and facultative anaerobes which are positive in the catalase test. The coagulase test is used to broadly demarcate *Staphylococcus* species into coagulase positive and coagulase negative species. *Staphylococcus species* grow readily on ordinary media with a temperature range of 10 to 40°C, the optimum being 37°C and a pH of 7.4-7.6. *Staphylococcus species* have emerged resistant to the penicillinase-stable penicillins (cloxacillin, dicloxacillin, methicillin, nafcillin, and oxacillin).

Klebsiella species

The genus *Klebsiella* consists of non-motile, capsulated rods that grow well on ordinary media forming large, dome shaped, mucoid colonies of varying degrees of stickiness. *Klebsiella species* are widely distributed in nature, occurring both as commensals in the intestines and as saprophytes in soil and water. *Klebsiella species* can cause diseases like pneumonia, ozena and rhinoscleroma.

Salmonella typhi

Salmonella typhi is a rod shaped flagellated gram negative organisms, that causes systemic infections and typhoid fever in humans.

Pseudomonas aeruginosa

Pseudomonas aeruginosa is a common gram negative, rod shaped bacterium that cause disease in plants and animals. It is an opportunistic human pathogen.

Characterization of nanoparticles

UV-Vis spectroscopy

The periodic scans of the optical absorbance between 345 and 700 nm with a UV- Vis spectrophotometer (Model 118, Systronics, Mumbai, India) at a resolution of 1 nm were performed to investigate the reduction rate of green synthesised nanoparticles. Deionised water was used to adjust the baseline.

The reduction of Ag^+ , Cu^{2+} and Zn^{2+} was monitored periodically by using a UV- Vis Spectrophotometer and the UV- Vis spectra of the reaction solutions were measured in the range of 375–760 nm.

SEM-XRD analysis

SEM-EDX Analysis was carried out in instrument JSM 6390 with acceleration voltage 20kV. SEM reveals information about the sample including external morphology, chemical composition and crystalline structure and orientation of materials making up the sample. SEM provides detailed high-resolution images of the sample by rastering a focused electron beam across the surface and detecting secondary or back scattered electron signal. The XRD imaging of the silver, copper and zinc nanoparticles was performed to confirm the presence of elemental metal signal and provides quantitative compositional information.

Antibacterial assay

Antimicrobial assay was performed by agar well diffusion method. The broth cultures of each organism were aseptically swabbed on Muller Hinton agar plates using sterile cotton swabs. Wells of 7 mm diameter were made in the inoculated plates using sterile cut tips and wells are filled with 20, 40 and 60 μ l of nanoparticle solution and 20 μ l of control (stock solution) and sample

(seed extract). The plates were incubated at 37°C for 24 hours after which the diameter of zones of inhibition were measured.

Statistical analysis

The results were analyzed and descriptive statistics were done using SPSS 12.0 (SPSS Inc., an IBM Company, Chicago, USA) and graphs were generated using Sigma Plot 7 (Systat Software Inc., Chicago, USA).

Results and Discussion

Synthesis of nanoparticles

Silver nanoparticles

To synthesize silver nanoparticles, seed extracts of different plants (Papaya and Mullatha separately) was added to 1mM silver nitrate solution and kept to reaction takes place. A colour change was observed from colourless to dark brown. This occurred due to the reduction of silver ions present in the solution. Synthesized silver nanoparticles were characterized by UV-VIS Spectrophotometry. The maximum peak was found to be 435 nm (λ max) for *Pouteria campechiana* and *Cycas circinalis*. The intensity of the peak at 435 nm was increased with time until the reduction completes. The maximum peak was found to be 385 nm (λ max) for *Carica papaya*, *Passiflora edulis* and *Annona muricata*. The intensity of the peak at 385 nm was increased with time until the reduction completes.

Copper nanoparticles

To synthesize copper nanoparticles, seed extracts of different plants (Papaya and Mullatha separately) was added to 100 mM Copper sulphate solution and kept to reaction takes place. A color change was observed from blue to pale yellow. This occurred due to the reduction of copper ions present in the solution. Synthesized copper nanoparticles were characterized by UV-VIS Spectrophotometry. The maximum peak was found to be 680 nm (λ max) for *Pouteria campechiana*, *Cycas circinalis*, *Carica papaya*, *Passiflora edulis* and *Annona muricata*. The intensity of the peak at 680 nm was increased with time until the reduction completes.

Zinc nanoparticles

To synthesize zinc nanoparticles, seed extracts of different plants (Papaya and Mullatha separately) was

added to 100 mM zinc Sulphate solution and kept at room temperature for reaction takes place. A colour change was observed from colourless to pale brown. This occurred due to the reduction of zinc ions present in the solution. Synthesized zinc nanoparticles were characterized by UV-VIS Spectrophotometry. The maximum peak was found to be 350 nm (λ max) for *Pouteria campechiana*, *Cycas circinalis*, *Carica papaya*, *Passiflora edulis* and *Annona muricata*. The intensity of the peak at 350 nm was increased with time until the reduction completes.

Antibacterial assay

Seed extracts of Papayand Mullatha showed growth inhibitory effects against *Salmonella Typhi*, *Pseudomonas aeruginosa*, *Staphylococcus aureus*, *E. coli* and *Klebsiella pneumoniae*.

For *Carica Papaya*, the zone of inhibition showed for *Salmonella* species, *Pseudomonas* species, *Staphylococcus* species, *E. coli* and *Klebsiella* species by silver nanoparticles formed from 20 μ l concentration of nanoparticles were 10 mm, 12 mm, 10 mm, 10 mm & 10 mm respectively; from 40 μ l concentration of nanoparticles were 12 mm, 15 mm, 11 mm, 12 mm & 11 mm respectively; from 60 μ l concentration of nanoparticles were 13 mm, 16 mm, 12 mm, 13 mm & 12 mm respectively. The zone of inhibition showed by *Salmonella* species, *Pseudomonas* species, *Staphylococcus* species, *E. coli* and *Klebsiella* species by seed extract was 9 mm, 9 mm, 10 mm, 7 mm & 8 mm respectively.

The zone of inhibition showed by *Salmonella* species, *Pseudomonas* species, *Staphylococcus* species, *E. coli* and *Klebsiella* species by copper nanoparticles formed from 20 μ l concentration of nanoparticles were 14 mm, 13 mm, 24 mm, 15 mm & 14 mm respectively; from 40 μ l concentration of nanoparticles were 17 mm, 14 mm, 27 mm, 18 mm & 18 mm respectively; from 60 μ l concentration of nanoparticles were 21 mm, 17 mm, 30 mm, 21 mm & 24 mm respectively. The zone of inhibition showed by *Salmonella* species, *Pseudomonas* species, *Staphylococcus* species, *E. coli* and *Klebsiella* species by zinc nanoparticles formed from 20 μ l concentration of nanoparticles were 21 mm, 12 mm, 22 mm, 20 mm & 23 mm respectively; from 40 μ l concentration of nanoparticles were 24 mm, 14 mm, 26 mm, 22 mm & 25 mm respectively; from 60 μ l concentration of nanoparticles were 26 mm, 16 mm, 30 mm, 25 mm & 28 mm respectively.

Table.1 Different vernacular names of Mullatha (*Annona muricata*) around the globe and India.

Language	Names
Scientific names	<i>Annona muricata</i>
Name in various global languages	
French	Anone
German	Anona
English	Soursop
Name in various Indian languages	
Sanskrit	
Hindi	
Urdu	
Marathi	
Kannada	Mulluramphal
Telugu	Lakshmanaphalamu
Malayalam	Mullatha
Tamil	MulluSeethaapazham

Table.2 Different vernacular names of Papaya (*Carica papaya*) around the globe and India.

Language	Names
Scientific names	<i>Carica papaya</i>
Name in various global languages	
French	Papaye
German	Papaya
English	Papaya
Name in various Indian languages	
Sanskrit	ErandKarkati
Hindi	Papita
Urdu	
Marathi	Pappayi
Kannada	
Gujarati	
Malayalam	Kappanga
Tamil	Pappali

Table.3 Zone of inhibition against various bacteria (*E. coli*, *Klebsiella species*, *Pseudomonas aeruginosa*, *Salmonella typhi* and *Staphylococcus aureus*) using nanoparticles produced by *Annona muricata* seed extract.

Microorganism	Nanoparticles	Control	Sample	Measure of zone of inhibition in mm		
				20	40	60
<i>E.coli</i>	Silver	10	8	11	13	15
	Copper	10	9	11	12	14
	Zinc	20	9	30	33	35
<i>Klebsiella species</i>	Silver	9	-	11	12	14
	Copper	9	9	10	10	11
	Zinc	11	10	22	24	25
<i>Pseudomonas aeruginosa</i>	Silver	10	-	11	12	13
	Copper	10	-	9	10	11
	Zinc	15	9	16	22	26
<i>Salmonella typhi</i>	Silver	10	8	13	16	20
	Copper	10	9	11	12	13
	Zinc	18	9	19	22	23
<i>Staphylococcus aureus</i>	Silver	13	8	14	15	17
	Copper	9	-	9	10	11
	Zinc	23	8	24	26	28

Table.4 Zone of inhibition against various bacteria (*E. coli*, *Klebsiella species*, *Pseudomonas aeruginosa*, *Salmonella typhi* and *Staphylococcus aureus*) using nanoparticles produced by *Carica papaya* seed extract.

Microorganism	Nanoparticles	Control	Sample	Measure of zone of inhibition in mm		
				20	40	60
<i>E.coli</i>	Silver	11	7	10	12	13
	Copper	14	12	15	18	21
	Zinc	17	11	20	22	25
<i>Klebsiella species</i>	Silver	10	8	10	11	12
	Copper	14	11	14	18	24
	Zinc	17	10	23	25	28
<i>Pseudomonas aeruginosa</i>	Silver	9	8	12	15	16
	Copper	10	8	13	14	17
	Zinc	11	9	12	14	16
<i>Salmonella typhi</i>	Silver	9	-	10	12	13
	Copper	15	9	14	17	21
	Zinc	18	12	21	24	26
<i>Staphylococcus aureus</i>	Silver	10	-	10	11	12
	Copper	20	13	24	27	30
	Zinc	20	9	22	26	30

Table.5 UV absorption spectrum of Silver nanoparticles formed from Papaya during different time of incubation.

Time	385 nm	435nm	560nm	680nm
½ hr	1.222	0.970	0.669	0.492
1 hr	1.240	1.003	0.710	0.527
1 ½ hr	1.264	1.029	0.753	0.557
2 hr	1.272	1.051	0.800	0.598
2 ½ hr	1.284	1.068	0.826	0.608
Blank	0.414	0.354	0.208	0.108

Table.6 UV absorption spectrum of Copper nanoparticles formed from Papaya during different time of incubation.

Time	385 nm	435nm	560nm	680nm
½ hr	0.201	0.179	0.268	0.618
1 hr	0.318	0.255	0.280	0.666
1 ½ hr	0.360	0.350	0.284	0.728
2 hr	0.381	0.386	0.341	0.753
2 ½ hr	0.389	0.421	0.354	0.765
Blank	0.039	0.033	0.044	0.471

Table.7 UV absorption spectrum of Zinc nanoparticles formed from Papaya during different time of incubation.

Time	350 nm	385 nm	435 nm	560 nm
½ hr	0.756	0.576	0.408	0.260
1 hr	0.764	0.578	0.412	0.280
1 ½ hr	0.816	0.591	0.453	0.282
2 hr	0.866	0.640	0.466	0.305
2 ½ hr	0.894	0.684	0.490	0.316
Blank	0.000	0.000	0.000	0.000

Table.8 Description of UV absorption spectrum of Silver nanoparticles formed from Mullatha during different time of incubation.

Time	385 nm	435nm	560nm	680nm
½ hr	1.359	1.204	0.920	0.716
1 hr	1.370	1.223	0.928	0.746
1 ½ hr	1.388	1.255	0.954	0.773
2 hr	1.428	1.318	0.981	0.776
2 ½ hr	1.480	1.396	1.052	0.810
Blank	0.414	0.354	0.208	0.108

Table.9 Description of UV absorption spectrum of Copper nanoparticles formed from Mullatha during different time of incubation.

Time	385 nm	435nm	560nm	680nm
½ hr	0.145	0.140	0.173	0.599
1 hr	0.157	0.161	0.256	0.708
1 ½ hr	0.295	0.250	0.267	0.724
2 hr	0.328	0.262	0.274	0.734
2 ½ hr	0.422	0.361	0.275	0.746
Blank	0.039	0.033	0.044	0.471

Table.10 Description of UV absorption spectrum of Copper nanoparticles formed from Mullatha during different time of incubation.

Time	350 nm	385 nm	435 nm	560 nm
½ hr	0.781	0.671	0.570	0.440
1 hr	0.857	0.718	0.600	0.444
1 ½ hr	0.901	0.790	0.677	0.514
2 hr	0.920	0.793	0.690	0.515
2 ½ hr	1.012	0.878	0.724	0.527
Blank	0.000	0.000	0.000	0.000

Table.11 Biochemical characterization of the organisms used in the study.

Organisms	I	MR	VP	C	GS	U	O	CL	COG	NR
<i>Salmonella typhi</i>	-VE	+VE	-VE	-VE	-VE	-VE	-VE	+VE	_	+VE
<i>Pseudomonas aeruginosa</i>	-VE	-VE	-VE	+VE	-VE	-VE	+VE	+VE	-VE	+VE
<i>Staphylococcus aureus</i>	-VE	+VE	+VE	+VE	+VE	+VE	-VE	+VE	+VE	+VE
<i>E. coli</i>	+VE	+VE	-VE	-VE	-VE	-VE	-VE	+VE	_	+VE
<i>Klebsiella pneumoniae</i>	-VE	-VE	+VE	+VE	-VE	+VE	-VE	+VE	_	+VE

(I- Indole, MR- Methyl Red, VP- Voges Proskauer, C- Citrate, GS- Gram Staining, U- Urease, O- Oxidase, CL- Catalase, COG- Coagulase, NR- Nitrogen Reductase).

Table.12 Antibiotic susceptibility test of the organisms used in the study.

Organisms	Zone of Inhibition (mm)							
	AMP	CHL	ENO	ERY	GEN	KAN	PEN	TET
<i>Salmonella typhi</i>	1.7	3.2	_	_	_	_	_	1.17
<i>Pseudomonas aeruginosa</i>	_	_	22-28	_	16-21	-	_	_
<i>Staphylococcus aureus</i>	27-35	19-26	22-28	22-30	19-27	19-26	26-37	24-30
<i>E. coli</i>	16-22	21-27	28-36	_	19-26	17-25	_	18-25
<i>Klebsiella pneumoniae</i>	32	_	_	16	_	_	16	14

Fig.1 Map of Kerala showing the various sample collection points.

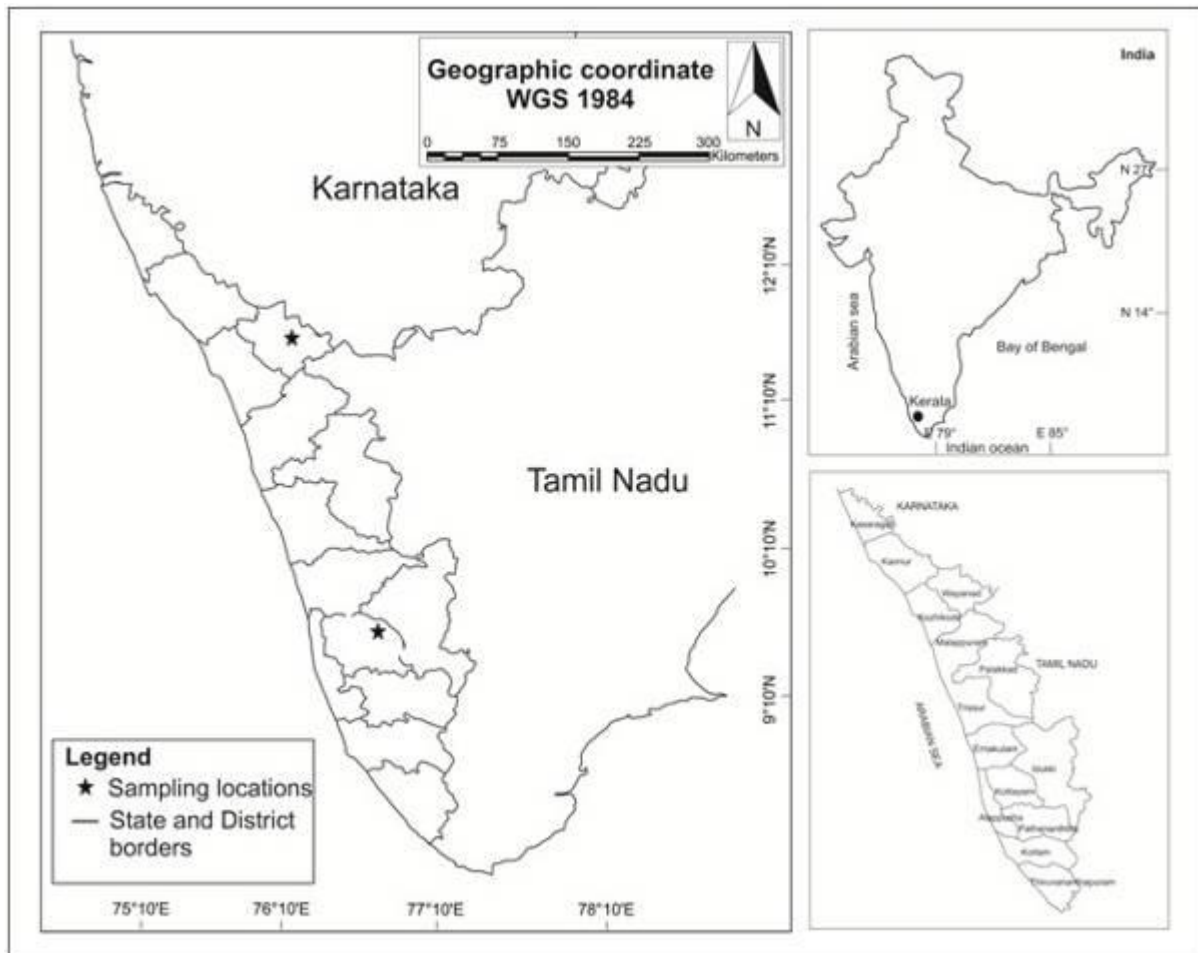


Fig.2 Description of Mullatha (*Annona muricata*) a) fruit cut opened, b) flower, c) fruit hanging in tree. Photo courtesy: Wikipedia.

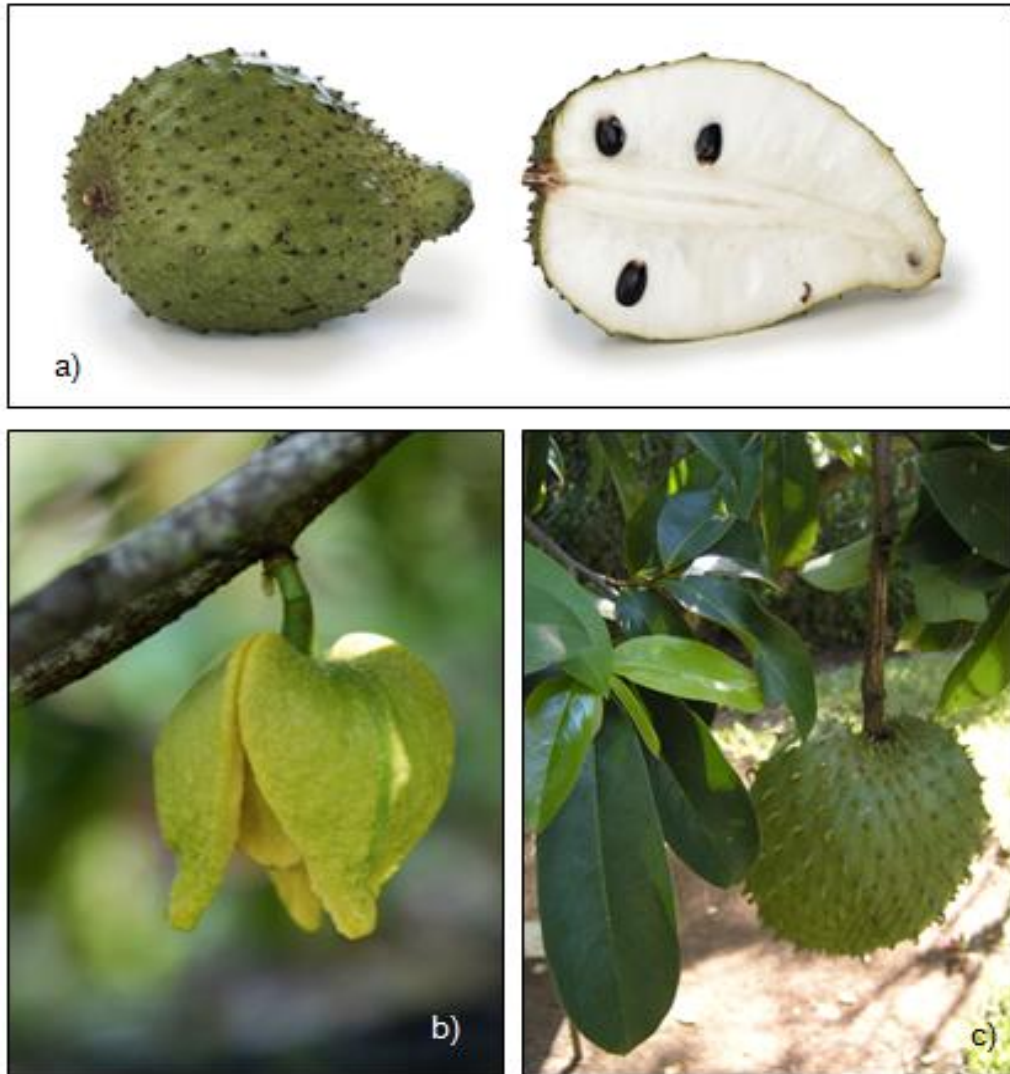


Fig.3 Papaya (*Carica papaya*) description a) different parts of the tree, b) fruit cut opened, c) tree bearing half mature fruits, d) tree bearing ripe and half mature fruits, e) female flower. Photo courtesy: Wikipedia.

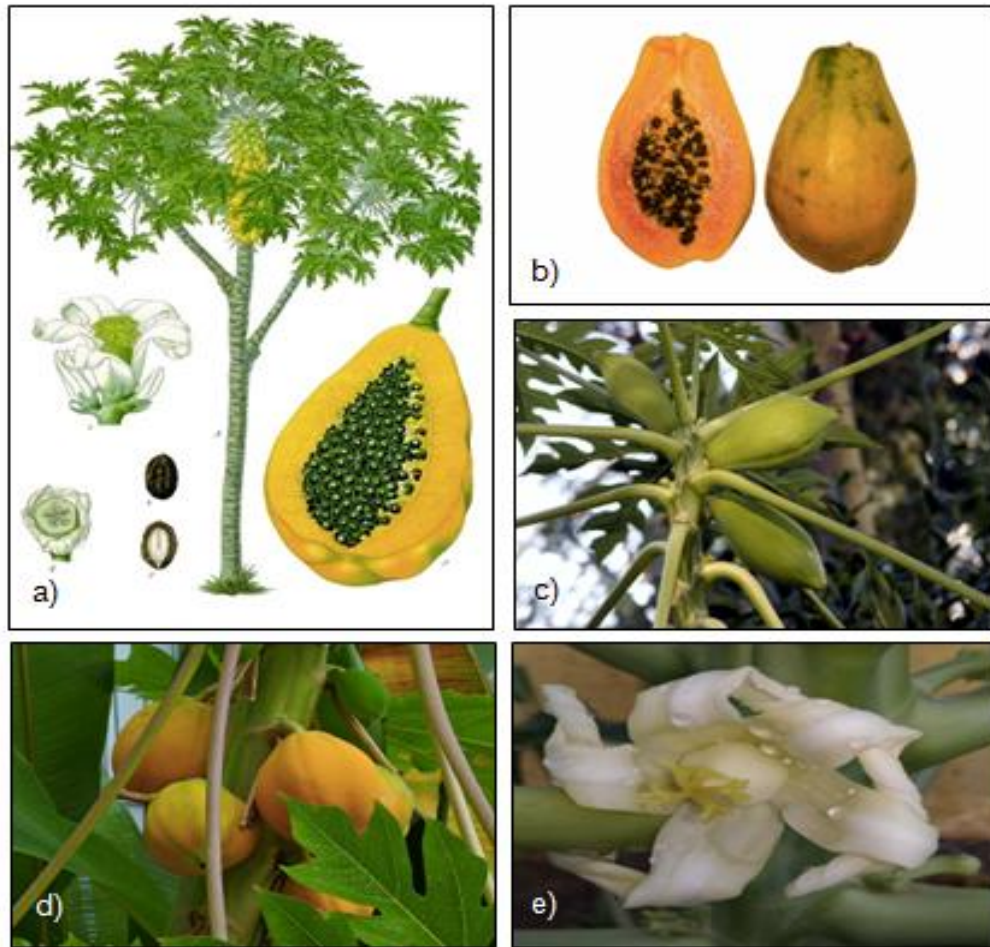


Fig.4 Description of the seeds used for making nanoparticles a) Mullatha (*Annona muricata*) seeds, b) Passion fruit (*Passiflora edulis*) seeds*, c) Eenth (*Cycas circinalis*)seeds*, d) Papaya (*Carica papaya*) seeds, e) Egg fruit (*Pouteria campechiana*) seeds*. * data not provided.



Fig.5 Antibacterial activity study using well diffusion method of Papaya plant seed extract nanoparticles (Cu) and (Ag) a) *Salmonella typhi* control plate (Cu), b) *Salmonella typhi* green synthesised nanoparticle test plate (Cu; 20, 40 and 60 μ l), c) *Pseudomonas aeruginosa* control, d) *Pseudomonas aeruginosa* test, e) *E. coli* control, f) *E. coli* test, g) *Klebsiella species* control, h) *Klebsiella species* test, i) *Staphylococcus species* control, j) *Staphylococcus species* test, k) to t) above mentioned organisms plate in same order for Ag nanoparticles.

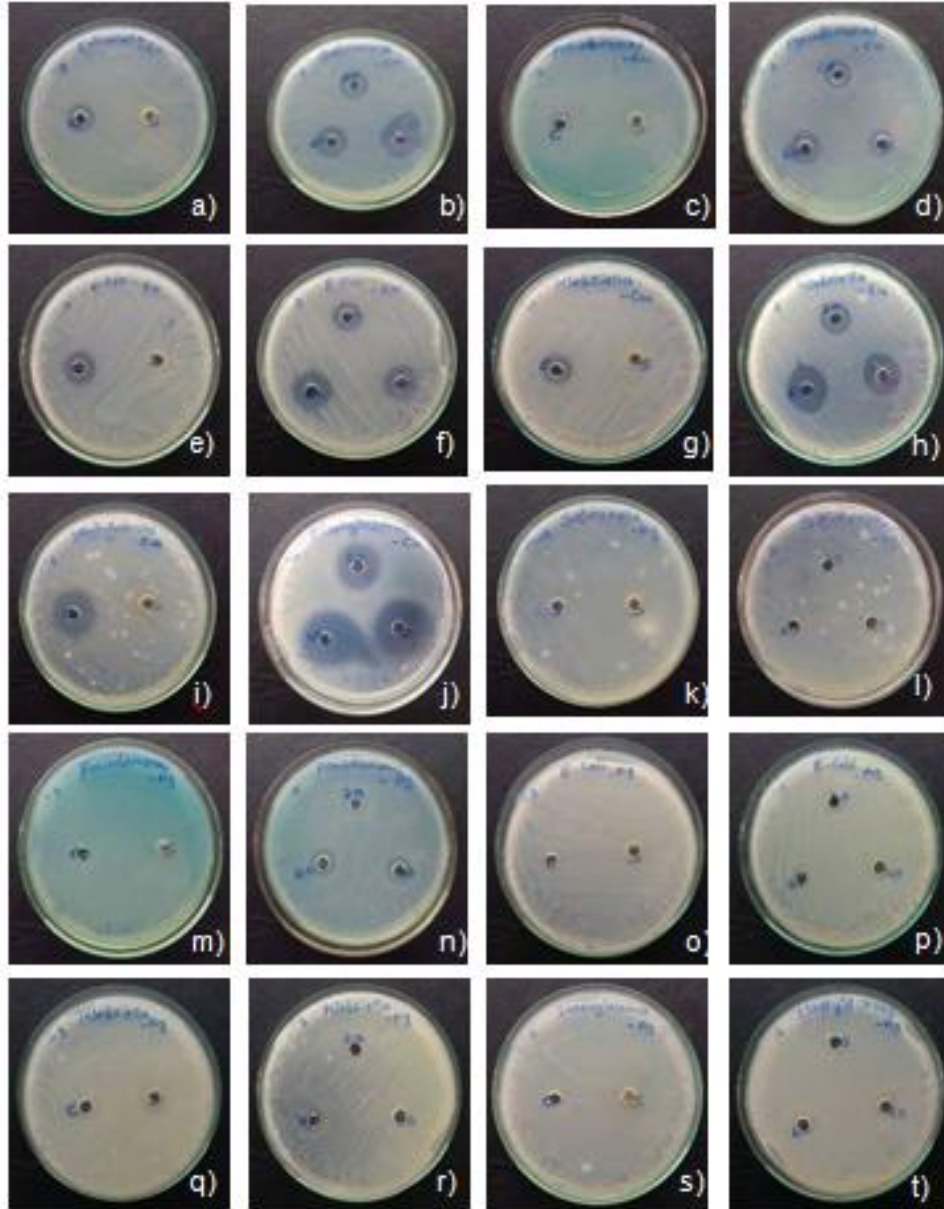


Fig.6 Antibacterial activity study using well diffusion method of Papaya plant and Passion fruit seed extract nanoparticles (Zn) and (Cu) a) *Salmonella typhi* control plate (Zn), b) *Salmonella typhi* green synthesised nanoparticle test plate (Zn; 20, 40 and 60 μ l), c) *Pseudomonas aeruginosa* control, d) *Pseudomonas aeruginosa* test, e) *E. coli* control, f) *E. coli* test, g) *Klebsiella species* control, h) *Klebsiella species* test, i) *Staphylococcus species* control, j) *Staphylococcus species* test, k) to t) above mentioned organisms plate in same order for Cu nanoparticles (Passion fruit).

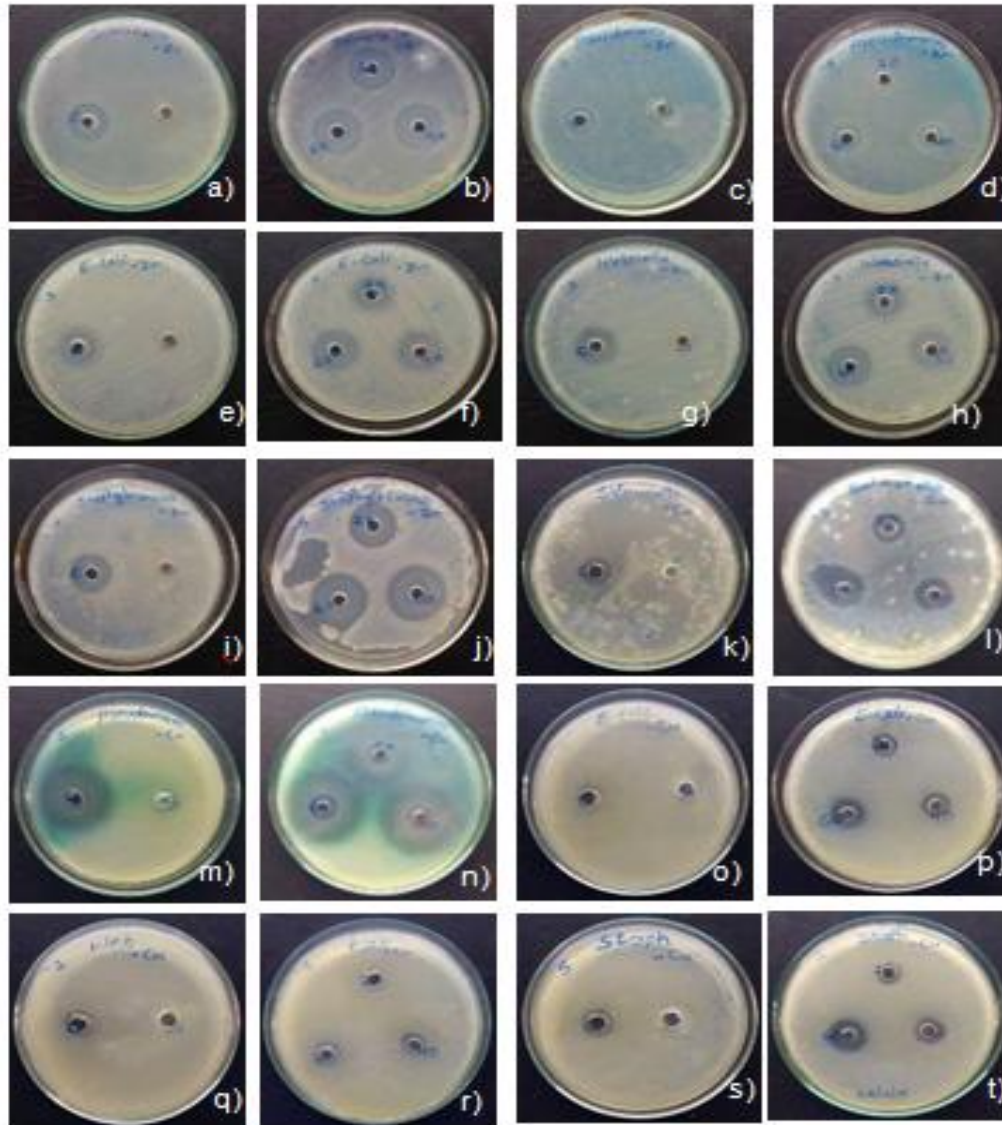


Fig.7 Antibacterial activity study using well diffusion method of Mullatha seed extract nanoparticles (Cu) and (Ag) a) *Salmonella typhi* control plate (Cu), b) *Salmonella typhi* green synthesised nanoparticle test plate (Cu; 20, 40 and 60 μ l), c) *Pseudomonas aeruginosa* control, d) *Pseudomonas aeruginosa* test, e) *E. coli* control, f) *E. coli* test, g) *Klebsiella species* control, h) *Klebsiella species* test, i) *Staphylococcus species* control, j) *Staphylococcus species* test, k) to t) above mentioned organisms plate in same order for Ag nanoparticles.


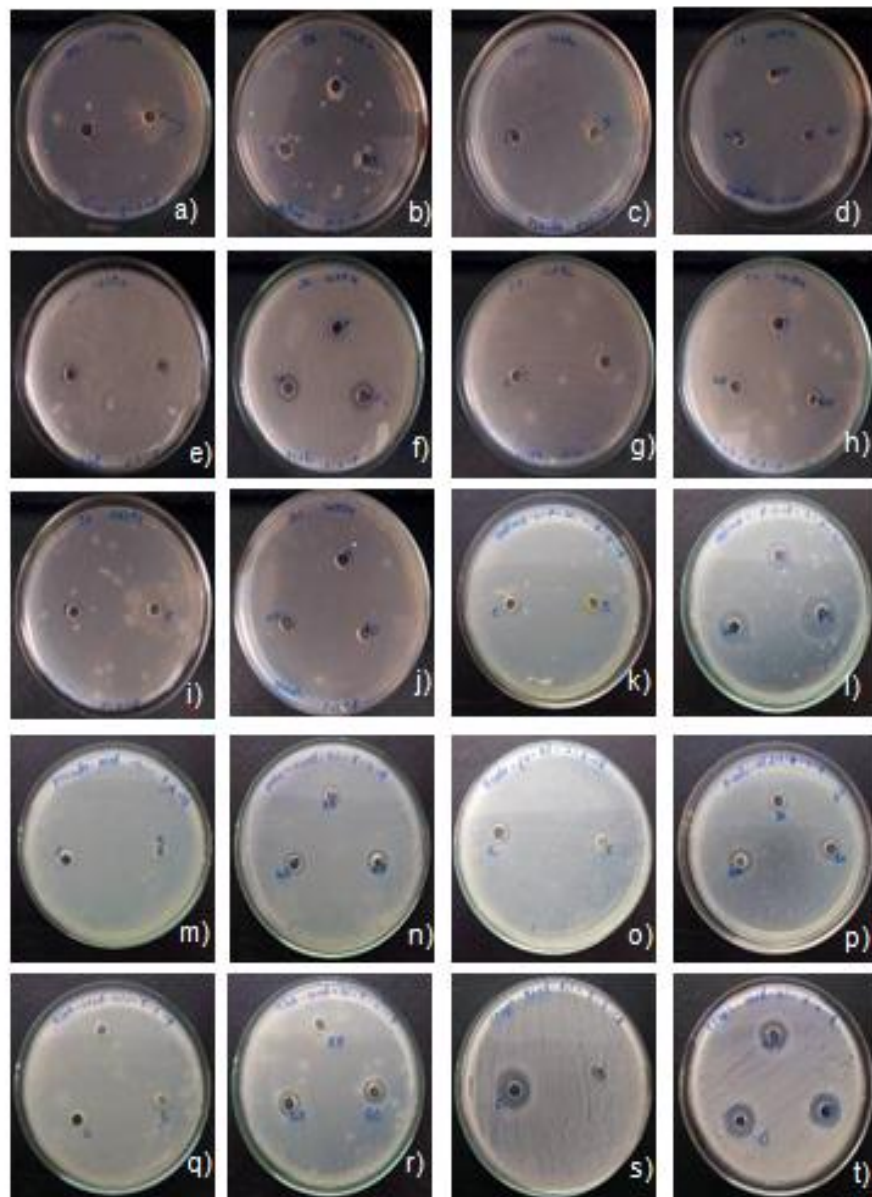


Fig.8 Antibacterial activity study using well diffusion method of Mullatha seed extract nanoparticles (Zn) a) *Salmonella typhi* control plate (Cu), b) *Salmonella typhi* green synthesised nanoparticle test plate (Cu; 20, 40 and 60 μ l), c) *Pseudomonas aeruginosa* control, d) *Pseudomonas aeruginosa* test, e) *E. coli* control, f) *E. coli* test, g) *Klebsiella species* control, h) *Staphylococcus species* test, i) *Staphylococcus species* control, j) *Klebsiella species* test.

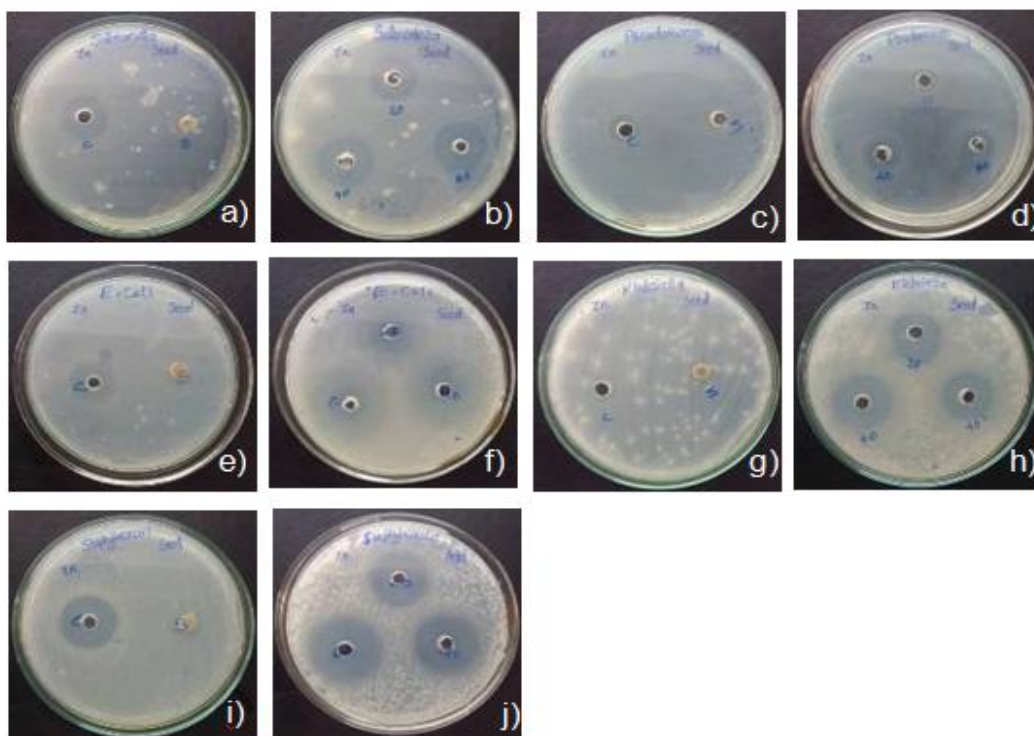

For *Annona Muricata*, the zone of inhibition showed for *Salmonella* species, *Pseudomonas* species, *Staphylococcus* species, *E. coli* and *Klebsiella* species by silver nanoparticles formed from 20 μ l concentration of nanoparticles were 13 mm, 11 mm, 14 mm, 11 mm & 11 mm respectively; from 40 μ l concentration of nanoparticles were 16 mm, 12 mm, 15 mm, 13 mm & 12 mm respectively; from 60 μ l concentration of nanoparticles were 20 mm, 13 mm, 17 mm, 15 mm & 14 mm respectively.

The zone of inhibition showed by *Salmonella* species, *Pseudomonas* species, *Staphylococcus* species, *E. coli* and *Klebsiella* species by seed extract was 9 mm, 9 mm, 8 mm, 9 mm & 10 mm respectively.

The zone of inhibition showed by *Salmonella* species, *Pseudomonas* species, *Staphylococcus* species, *E. coli* and *Klebsiella* species by copper nanoparticles formed from 20 μ l concentration of nanoparticles were 11 mm, 9 mm, 9 mm, 11 mm & 10 mm respectively; from 40 μ l concentration of nanoparticles were 12 mm, 10 mm, 10 mm, 12 mm & 11 mm respectively; from 60 μ l

concentration of nanoparticles were 13 mm, 11 mm, 11 mm, 14 mm & 12 mm respectively.

The zone of inhibition showed by *Salmonella* species, *Pseudomonas* species, *Staphylococcus* species, *E. coli* and *Klebsiella* species by zinc nanoparticles formed from 20 μ l concentration of nanoparticles were 19 mm, 16 mm, 24 mm, 30 mm & 22 mm respectively; from 40 μ l concentration of nanoparticles were 22 mm, 22 mm, 26 mm, 33 mm & 24 mm respectively; from 60 μ l concentration of nanoparticles were 23 mm, 26 mm, 28 mm, 35 mm & 25 mm respectively.

Silver, copper and zinc nanoparticles have antibacterial activity against *Salmonella* species, *Pseudomonas* species, *Staphylococcus* species, *E. coli* and *Klebsiella* species. When antibacterial activity of silver, copper and zinc nanoparticles from 3 different concentrations were observed, nanoparticles have 60 μ l concentration shows maximum activity against these microbes.

Silver nanoparticles shows greater antibacterial activity compared to silver nitrate and seed extract. Copper

nanoparticles shows greater antibacterial activity compared to copper Sulphate and seed extract. Zinc nanoparticles shows greater antibacterial activity compared to zinc Sulphate and seed extract. Maximum zone of inhibition was at 60 μ l for all the bacterial cultures. It indicates that zone of inhibition increases as the concentration of nanoparticles increased.

SEM-XRD analysis

The SEM-XRD analysis proved the effective formation of silver, copper and zinc nanoparticles in all the samples.

The results showed that seed extracts of *Carica papaya* and *Annona muricata* are used to the synthesis of silver, copper and zinc nanoparticles. The synthesized silver, copper and zinc nanoparticles shows antibacterial activity on both Gram positive and Gram negative bacteria. This biosynthesis of nanoparticles is cost efficient, pollutant free and simpler to synthesize.

Acknowledgements

The authors are grateful for the cooperation of the management of Mar Augusthinose college for necessary support. Technical support from Binoy A Mulantra is also acknowledged.

References

Ayoola, P. B., & Adeyeye, A. (2010). Phytochemical and nutrient evaluation of *Carica papaya* (PAWPAW) leaves. *IJRRAS*5(3), 325-328.

Balouiri, M., Germano, M. P., & Nostro, A. R. (2016). Methods for in vitro evaluating antimicrobial activity. A review. *Journal of Pharmaceutical Analysis*, 6(2), 71-79.

Braydich-Stolle, L., Hussain, S., Schlager, J. J., & Hofmann, M. C. (2005). In vitro cytotoxicity of nanoparticles in mammalian germline stem cells. *Toxicological sciences*, 88(2), 412-419.

Burd, A., Kwok, C. H., Hung, S. C., Chan, H. S., Gu, H., Lam, W. K., & Huang, L. (2007). A comparative study of the cytotoxicity of silver-based dressings in monolayer cell, tissue explant, and animal models. *Wound repair and regeneration*, 15(1), 94-104.

Danilczuk, M., Lund, A., Sadlo, J., Yamada, H., & Michalik, J. (2006). Conduction electron spin resonance of small silver particles. *Spectrochimica Acta Part A: Molecular and Biomolecular Spectroscopy*, 63(1), 189-191.

Duran, N., Marcata, P. D., Alves, O. L., & Esposito, E. (2017). Antibacterial effect of silver nanoparticles produced by fungal process on textile fabrics and their effluent treatments. *Journal of Biomedical Nanotechnology*, 3(2), 203-208.

Elechiguerra, J. L., Burt, J. L., Morones, J. R., Bragado, A. C., Gao, x., Lara, H. L., & Yacamán, M. J. (2005). Interaction of silver nanoparticles with HIV-1. *Journal of Nanobiotechnology*, 3(6), 1-10.

El-Rafie, M. H., Mohamed, A. A., Shaheen, T. I., & Hebeish, A. (2010). Antimicrobial effect of silver nanoparticles produced by fungal process on cotton fabrics. *Carbohydrate Polymers*, 80(3), 779-782.

Feng, Q. L., Wu, J., Chen, G. Q., Cui, F. Z., Kim, T. N., & Kim, J. O. (2000). A mechanistic study of the antibacterial effect of silver ions on *Escherichia coli* and *Staphylococcus aureus*. *Journal of biomedical materials research*, 52(4), 662-668.

Feng, Q. L., Wu, J., Chen, G. Q., Cui, F. Z., Kim, T. N., & Kim, J. O. (2000). A mechanistic study of the antibacterial effect of silver ions on *Escherichia coli* and *Staphylococcus aureus*. *Journal of biomedical materials research*, 52(4), 662-668.

Fox, C. L., & Modak, S. M. (1974). Mechanism of silver sulfadiazine action on burn wound infections. *Antimicrobial agents and chemotherapy*, 5(6), 582-588.

Furno, F., Morley, K. S., Wong, B., Sharp, B. L., Arnold, P. L., Howdle, S. M.,... & Reid, H. J. (2004). Silver nanoparticles and polymeric medical devices: a new approach to prevention of infection?. *Journal of Antimicrobial Chemotherapy*, 54(6), 1019-1024.

Gong, P., Li, H., He, X., Wang, K., Hu, J., Tan, W.,... & Yang, X. (2007). Preparation and antibacterial activity of Fe₃O₄@ Ag nanoparticles. *Nanotechnology*, 18(28), 285604.

Guggenbichler, J. P., Böswald, M., Lugauer, S., & Krall, T. (1999). A new technology of microdispersed silver in polyurethane induces antimicrobial activity in central venous catheters. *Infection*, 27(1), S16-S23.

Gupta, A., & Silver, S. (1998). Molecular genetics: silver as a biocide: will resistance become a problem?. *Nature biotechnology*, 16(10), 888.

Hajipour, M. J., Fromm, K. M., Ashkarran, A. A., Aberasturi, D. J., Larramendi, I. R., Rojo, T., Serpooshan, V., Parak, W. J., & Mahmoudi, Morteza (2012). Antibacterial properties of nanoparticles. *Trends in Biotechnology* doi: 10.1016/j.tibtech.2012.06.004, 2012.

Hajipour, M. J., Fromm, K. M., Ashkarran, A. A., de Aberasturi, D. J., de Larramendi, I. R., Rojo, T.,... & Mahmoudi, M. (2012). Antibacterial properties of nanoparticles. *Trends in biotechnology*, 30(10), 499-511.

- Hernandez, C. L. C., Villasenor, I. M., Joseph, E., & Tolliday, N. (2008). Isolation and evaluation of antimicrobial activity of phenolic compounds from *Pouteria campechiana*. *Philippine Journal of Science*, 137(1), 1-10.
- Hussain, S. M., Hess, K. L., Gearhart, J. M., Geiss, K. T., & Schlager, J. J. (2005). In vitro toxicity of nanoparticles in BRL 3A rat liver cells. *Toxicology in vitro*, 19(7), 975-983.
- Ip, M., Lui, S. L., Poon, V. K., Lung, I., & Burd, A. (2006). Antimicrobial activities of silver dressings: an in vitro comparison. *Journal of Medical Microbiology*, 55(1), 59-63.
- Jagessar, R. C., Hafeez, A., Chichester, M., & Crepaul, Y. (2017). Antimicrobial activity of the ethanolic and aqueous extract of passion fruit (*Passiflora edulis SIMS*), in the absence of $Zn(OAc)_2 \cdot 2H_2O$. *World Journal of Pharmacy and Pharmaceutical Sciences*, 6(9), 230-246.
- Jain, P., & Pradeep, T. (2005). Potential of silver nanoparticle-coated polyurethane foam as an antibacterial water filter. *Biotechnology and Bioengineering*, 90(1), 59-63.
- Kale, R., Barwar, S., Kane, P., & More, S. (2018). Green synthesis of silver nanoparticles using papaya seed and its characterization. *International Journal for Research in Applied Science and Engineering Technology*, 6(2), 168-174.
- Kalpashree, M. M., & Raveesha, K. A. (2013). Antibacterial activity of *Cycas circinalis* ovules- A naked seeded gymnosperm. *International Journal of Herbal Medicine*, 1(3), 53-55.
- Kim, J. S., Kuk, E., Yu, K. N., Kim, J. H., Park, S. J., Lee, H. J.,... & Kim, Y. K. (2007). Antimicrobial effects of silver nanoparticles. *Nanomedicine: Nanotechnology, Biology and Medicine*, 3(1), 95-101.
- Klueh, U., Wagner, V., Kelly, S., Johnson, A., & Bryers, J. D. (2000). Efficacy of silver-coated fabric to prevent bacterial colonization and subsequent device-based biofilm formation. *Journal of Biomedical Materials Research Part A*, 53(6), 621-631.
- Krishna, K. L., Paridhavi, M., & Patel, J. A. (2008). Review on nutritional, medicinal and pharmacological properties of papaya (*Carica papaya Linn*). *Natural Product Radiances*, 7(4), 364-373.
- Krishnakumar, K. N., Rao, G. P., & Gopakumar, C. S. (2009). Rainfall trends in twentieth century over Kerala, India. *Atmospheric Environment*, 43(11), 1940-1944.
- Kumar, A., Kumar, P., Ajayan, M. P., & John, G. (2008). Silver nanoparticles embedded antimicrobial paints based on vegetable oil. *Nature Materials*, 7(3), 236-241.
- Kumar, V., & Yadav, S. K. (2009). Plant mediated synthesis of silver and gold nanoparticles and their applications. *Journal of Chemical Technology and Biotechnology*, 84(2), 151-157.
- Kuppusamy, P., Yusoff, M. M., Maniam, G. P., & Govindan, N. (2014). Biosynthesis of metallic nanoparticles using plant derivatives and their new avenues in pharmacological applications-An updated report. *Saudi Pharmaceutical Journal*, 24, 473-484.
- Leaper, D. J. (2006). Silver dressings: their role in wound management. *International Wound Journal*, 3(4), 282-294.
- Li, X. Q., Elliott, D. W., & Zhang, W. X. (2006). Zero-valent iron nanoparticles for abatement of environmental pollutants: materials and engineering aspects. *Critical reviews in solid state and materials sciences*, 31(4), 111-122.
- Lok, C. N., Ho, C. M., Chen, R., He, Q. Y., Yu, W. Y., Sun, H.,... & Che, C. M. (2007). Silver nanoparticles: partial oxidation and antibacterial activities. *JBIC Journal of Biological Inorganic Chemistry*, 12(4), 527-534.
- Luo, X., Morrin, A., Killard, A. J., & Smyth, M. R. (2006). Application of nanoparticles in electrochemical sensors and biosensors. *Willey Online Library*, 18(4).
- Malacrida, C. R., & Jorge, N. (2012). Yellow passion fruit seed oil (*Passiflora edulis f. flavicarpa*): Physical and chemical characteristics. *Brazilian Archives of Biology and Technology*, 55(1), 127-134.
- Mehraj, H., Sikder, R. K., Mayda, U., Taufique, T., & Uddin, J. (2015). Plant physiology and fruit secondary metabolites of canistel (*Pouteria campechiana*). *World Applied Sciences Journal*, 33(12), 1908-1914.
- Mishra, Vijayalaxmee., Sharma, Richa., Jasuja, N. D., & Gupta, D. K. (2014). A review on green synthesis of nanoparticles and evaluation of antimicrobial activity. *International Journal of Green and Herbal Chemistry*, 3(1), 081-094.
- Morones, J. R., Elechiguerra, J. L., Camacho, A., Holt, K., Kouri, J. B., Ramirez, J. T., & Yacaman, M. J. (2005). The bactericidal effect of silver nanoparticles. *Nanotechnology*, 16(10), 2346.
- Muhamad, S. A. S., Jamilah, B., Russly, A. R., & Faridah, A. (2017). The antibacterial activities and chemical composition of extracts from *Carica papaya* cv. *Sekaki* / Hong Kong seed. *International Food Research Journal*, 24(2), 810-818.
- Nikawa, H., Yamamoto, T., Hamada, T., Rahardjo, M. B., Murata, H., & Nakanoda, S. (1997). Antifungal

- effect of zeolite-incorporated tissue conditioner against *Candida albicans* growth and/or acid production. *Journal of oral Rehabilitation*, 24(5), 350-357.
- Ong, H. T., Loo, J. S., Boey, F. Y., Russell, S. J., Ma, J., & Peng, K. W. (2008). Exploiting the high-affinity phosphonate–hydroxyapatite nanoparticle interaction for delivery of radiation and drugs. *Journal of Nanoparticle Research*, 10(1), 141-150.
- Pankhurst, Q. A., Connolly, J., Jones, S. K., & Dobson, J. (2003). Application of magnetic nanoparticles in biomedicine. *Journal of Physics D: Applied Physics*, 36(13), 167-181.
- Paul, N. S., & Yadav, R. P. (2015). Biosynthesis of silver nanoparticles using plant seeds and their antimicrobial activity. *Asian Journal of Biomedical and Pharmaceutical Sciences*, 5(45), 26-28.
- Paul, N. S., Sharma, R., & Yadav, R. P. (2015). Biological synthesis of antimicrobial silver nanoparticles by *Phaseolus vulgaris* seed extract. *MGM Journal of Medical Sciences*, 2(1), 1-6.
- Peter, J. K., Kumar, Y., Pandey, P., & Masih, H. (2014). Antibacterial activity of seed and leaf extract of *Carica papaya* var. *Pusa dwarf* Linn. *IOSR Journal of Pharmacy and Biological Sciences*, 9(2), 29-37.
- Prabu, H. J., & Johnson, I. (2015). Antibacterial activity of silver nanoparticles synthesized from plant leaf extract of *Cycas circinalis*, *Ficus amplissima*, *Commelina benghalensis* and *Lippia nodiflora* leaves. *Journal of Chemical and Pharmaceutical Research*, 7(9), 443-449.
- Prasad, B. L. V., Sorensen, C. M., & Klabunde, K. J. (2008). Gold nanoparticle superlattices. *Chemical Society Reviews*, 37(9), 1871-1883.
- Prasad, S., Singh, Mritunjai., Singh, Shinjini., & Gambhir, I. S. (2008). Nanotechnology in medicine and antibacterial effect of silver nanoparticles. *Digest Journal of Nanomaterials and Biostructures*, 3(3), 115-122.
- Prema, P. (2011). Chemical mediated synthesis of silver nanoparticles and its potential antibacterial application. In *Progress in Molecular and Environmental Bioengineering-From Analysis and Modeling to Technology Applications*. InTech.
- Rajeswari, D. V., Gajalakshmi, S., & Vijayalakshmi, S. (2012). Phytochemical and pharmacological properties of *Annona muricata*: A review. *International Journal of Pharmacy and Pharmaceutical Sciences*, 4(2), 3-6.
- Ramesh, B., Vijayameena, C., Subhashini, G., & Loganayagi, M. (2013). Phytochemical screening and assessment of antibacterial activity for the bioactive compounds in *Annona muricata*. *International Journal of Current Microbiology and Applied Sciences*, 2(1), 1-8.
- Sajeshkumar, N. K., Vazhacharickal, P. J., Mathew, J. J., & Joy, J. (2015b). Synthesis of silver nanoparticles from neem leaf (*Azadirachta indica*) extract and its antibacterial activity. *CIB Tech Journal of Biotechnology*, 4(2), 20-31.
- Sajeshkumar, N. K., Vazhacharickal, P. J., Mathew, J. J., & Sebastin, A. (2015a). Synthesis of silver nanoparticles from curry leaf (*Murraya koenigii*) extract and its antibacterial activity. *CIB Tech Journal of Pharmaceutical Sciences*, 4(2), 15-25.
- Salata, O. V. (2004). Applications of nanoparticles in biology and medicine. *Journal of Nanobiotechnology*, 2(1), 3-8.
- Showmya, J. J., Harini, K., Pradeepa, M., Thiyagarajan, M., Manikandan, R., Venkatachalam, P., & Geetha, N. (2012). Rapid green synthesis of silver nanoparticles using seed extract of *Foeniculum vulgare* and screening of its antibacterial activity. *Plant Cell Biotechnology and Molecular Biology*, 13(1-2), 31-38.
- Singh, S., (2017). Green approach towards synthesis of copper nanoparticles: A review. *International Journal of Innovative and Emerging Research in Engineering*, 4(7), 1-7.
- Yeo, S. Y., Lee, H. J., & Jeong, S. H. (2003). Preparation of nanocomposite fibers for permanent antibacterial effect. *Journal of Materials Science*, 38(10), 2143-2147.

How to cite this article:

Prem Jose Vazhacharickal and Jismon Thomas. 2022. Synthesis of Silver, Copper and Zinc Nanoparticles from *Carica papaya* and *Annona muricata*, Seeds and Evaluation of their Antibacterial Activity. *Int.J.Curr.Res.Aca.Rev.* 10(06), 5-26. doi: <https://doi.org/10.20546/ijcrar.2022.1006.002>